

This is an electronic reprint of the original article. This reprint may differ from the original in pagination and typographic detail.

Cellulosic fibers spun from stabilized imidazolium ionic liquids: identification of chromophores in the fibers after accelerated ageing

Rosenau, Thomas; Potthast, Antje; Zhang, Jiaping; Barbini, Stefano; Koide, Mitsuharu; Rinner, Uwe; Hettegger, Hubert

Published in:

Chemical Monthly / Monatshefte für Chemie

DOI:

[10.1007/s00706-024-03203-6](https://doi.org/10.1007/s00706-024-03203-6)

Published: 01/01/2025

Document Version

Final published version

Document License

CC BY

[Link to publication](#)

Please cite the original version:

Rosenau, T., Potthast, A., Zhang, J., Barbini, S., Koide, M., Rinner, U., & Hettegger, H. (2025). Cellulosic fibers spun from stabilized imidazolium ionic liquids: identification of chromophores in the fibers after accelerated ageing. *Chemical Monthly / Monatshefte für Chemie*, 156(1), 77-90. <https://doi.org/10.1007/s00706-024-03203-6>

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.



Cellulosic fibers spun from stabilized imidazolium ionic liquids: identification of chromophores in the fibers after accelerated ageing


Thomas Rosenau^{1,2} · Antje Potthast¹ · Jiaping Zhang³ · Stefano Barbini^{1,4} · Mitsuharu Koide¹ · Uwe Rinner⁵ · Hubert Hettegger^{1,6}

Received: 1 February 2024 / Accepted: 28 March 2024 / Published online: 11 April 2024
© The Author(s) 2024

Abstract

Cellulosic fibers spun from 1,3-dialkylimidazolium ionic liquids are effectively stabilized against cellulose degradation by the addition of antioxidants, but this protective effect comes at the expense of chromophore generation from the degradation products of the stabilizers. In this study, we identified the oxidation and degradation products of four natural antioxidants, α -tocopherol, *N*-methyl- α -tocopheramine, propyl gallate, and hydroxytyrosol, formed upon accelerated ageing of the fibers. Ageing was performed according to standard protocols under either dry or moist conditions and the extraction was done with supercritical carbon dioxide. Chromophore formation in spinning dope, upon dry ageing and moist ageing were compared. In total, 16 different oxidation/degradation products were isolated, their structure confirmed by comprehensive analytical characterization with full NMR resonance assignment in the ¹H and ¹³C domains as well as by comparison with authentic samples, and their formation pathways discussed. Knowledge of the chemical structures of the degradation products originating from the stabilizers now provides a good starting point for optimization of the fiber bleaching stage.

Graphical abstract

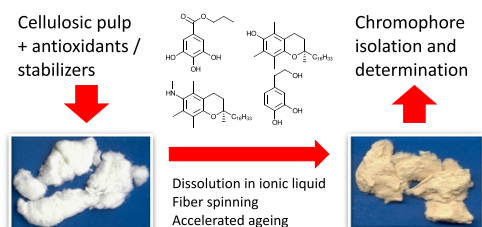

Keywords Cellulose · Ionic liquids · Fiber spinning · Antioxidants · Ageing · Bleaching · Chromophores

✉ Thomas Rosenau
thomas.rosenau@boku.ac.at

¹ Department of Chemistry, Institute of Chemistry of Renewable Resources, University of Natural Resources and Life Sciences, Vienna (BOKU), Muthgasse 18, 1190 Vienna, Austria

² Laboratory of Natural Materials Technology, Faculty of Science and Engineering, Åbo Akademi University, Porthansgatan 3, 20500 Åbo/Turku, Finland

³ Department of Materials Science and Engineering, Shinshu University, 3-15-1 Tokida, Ueda, Nagano 386-8567, Japan

⁴ Natex Prozesstechnologie GesmbH, R&D, 2630 Ternitz, Austria

⁵ Institute of Applied Chemistry, IMC Krems University of Applied Sciences, Piaristengasse 1, 3500 Krems, Austria


⁶ Christian Doppler Laboratory for Cellulose High-Tech Materials, University of Natural Resources and Life Sciences, Vienna (BOKU), Konrad-Lorenz-Strasse 24, 3430 Tulln, Austria

Introduction

The production of man-made cellulosic fibers by spinning from cellulose solutions has not only evolved into an important facet of sustainable materials science but is above all an economically significant factor and a mainstay of the pulp-based industries. Approximately two decades ago, ionic liquids, specifically *N*-alkyl-*N*-methylimidazolium ILs, have emerged as promising solvents for cellulose and potential pulping agents. However, the initial euphoria faded with unsurmountable challenges in recycling and purification, hindering their widespread adoption. Subsequent advancements in IL technology, particularly with higher-generation ionic liquids, addressed these challenges and culminated in the development of the Ioncell® technology [1–5] for cellulose dissolution and fiber spinning on a larger scale. Recently, also the first-generation ILs with 3-alkyl-1-methylimidazolium structure have regained attention in the quest for eco-friendly and efficient cellulose fiber production [6, 7], applied in the production of special high-strength cellulose fibers from pure pulps which overcome the usual recycling and purification hurdles. However, the inherent reactivity of these solvents [8, 9] and the involvement of oxidative processes during dope preparation, spinning, and fiber ageing pose considerable challenges, necessitating the use of stabilizers—which is the general topic of our investigation.

Despite the successful suppression of cellulose degradation during dissolution and fiber spinning through the incorporation of antioxidants, a concomitant issue arises—the formation of chromophores from the stabilizers—leading to discoloration of the spinning dope and the resultant fibers. Previous studies have demonstrated that the degradation of cellulose upon dissolution in 1,3-dialkylimidazolium ionic liquids, formation of a spinning dope, and spinning of cellulosic fibers from this dope, is mainly due to homolytic degradation reactions, i.e., processes that involve atmospheric oxygen [10] and radical oxygen species as shown by spin trapping [11]. The addition of antioxidants, commonly 2wt% relative to the dissolved pulp, can effectively curb these cellulose degradation reactions. This stabilization, however, comes at the cost of increased discoloration of the spinning dope. The resulting decrease in brightness of the spun fibers poses challenges in terms of bleachability, chemical needs for bleaching treatments and brightness stability. To tackle this issue, a deeper understanding of the chemical structures of the generated chromophores becomes imperative. Following green chemistry principles, the focus was on stabilizers from renewable resources rather than synthetic antioxidants. Luckily, the four natural antioxidants α -tocopherol (1), *N*-methyl- α -tocopheramine (2), propyl gallate (3), and

Scheme 1

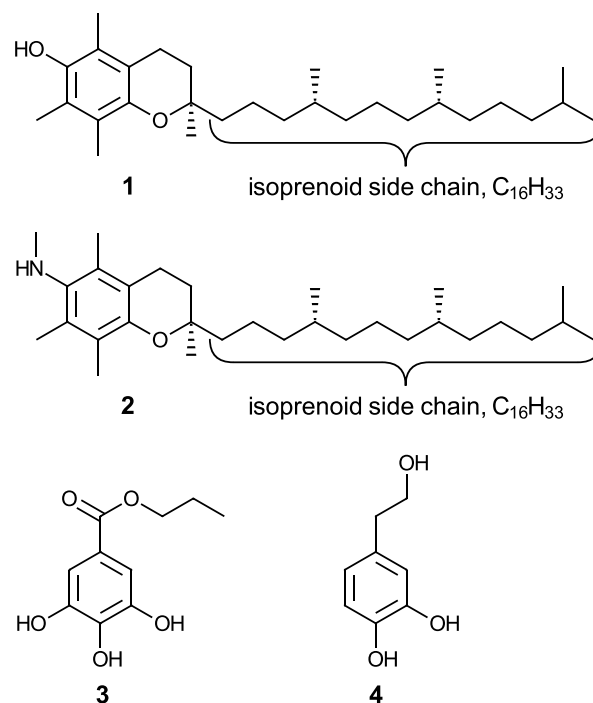

hydroxytyrosol (4), see Scheme 1, were among the stabilizers showing optimum overall performance in a comparison with 12 commercially available antioxidants [10].

They gave the best-balanced results with regard to minimizing side reactions in the spinning dope, minimizing cellulose degradation in the spinning dope and the spun fibers, and limiting chromophore generation in the spinning dope and resulting fibers. These four antioxidants have been studied in detail with regard to their protective effect in the spinning dope and the generation of oxidation products. The concomitant chromophore generation and discoloration can be counteracted by a fiber bleaching/washing step, an approach that is generally used in the manufacture of man-made cellulosic fibers, such as viscose (Rayon) or Lyocell fibers. In the case of the studied antioxidants, roughly one-third of the stabilizer amount is used up during dope preparation and spinning, the other two-thirds are incorporated into the fibers to prolong the shelf-life and for long-term stabilization of the cellulose.

In this study, we address the formation and identification of oxidation and degradation products of the antioxidants in the spun fibers upon long-term storage, in particular the chromophoric products. Long-term behavior is simulated by accelerated ageing under either dry or moist conditions according to standard procedures in cellulose fiber and paper science. The exact knowledge of the chemical structures of the reaction products is necessary on the one hand to exclude the formation of any unwanted harmful compounds and on the other hand to optimize the final bleaching step in the

fiber treatment with regard to effectivity, mild conditions, and chemical savings.

Results and discussion

Stabilizing effect of the antioxidant additives 1–4

The beneficial effect of the stabilizers can be demonstrated in a particularly striking way by comparing the celluloses' molar mass (M_w) of the stabilized fibers to a non-stabilized blank (Figs. 1 and 2). For all stabilized fibers the M_w values stayed above 85% of the initial pulp value, while there was a steep drop to about 50% in the case of the non-stabilized pulp. After 12 h of ageing, the stabilizers α -tocopherol (1), *N*-methyl- α -tocopheramine (2), and propyl gallate (3) had been largely consumed (see below), which is reflected by a sharper decrease of M_w in the interval between 12 and 24 h

than before. In the case of hydroxytyrosol (4), there was only a minor decrease between 12 and 24 h, comparable to the ageing period before, because the stabilizer was still abundantly present after 12 h (see below) and thus still ready to act. The M_w loss of the non-stabilized fibers between 12 and 24 h of ageing was drastic, dropping to approx. 30% of the starting pulp value. There was no significant difference between dry and wet ageing in the ageing behavior and stabilizing efficiency, although some mechanisms and product distributions were well dissimilar, as discussed below.

Figures 1 and 2 show the cellulose degradation upon spinning dope preparation (5 wt% cellulose in 1-ethyl-3-methylimidazolium acetate, EMIm-OAc) and subsequent dry and moist accelerated ageing of the spun fibers, in dependence on the added stabilizers (0.1 wt% rel. to dope, 2 wt% rel. to dissolved pulp). The molar mass, determined by gel permeation chromatography according to the standard protocol [12] is expressed as molar mass loss [%] relative to the starting

Fig. 1 Cellulose degradation (as molar mass loss relative to the starting pulp) upon spinning dope preparation and dry ageing over different times. Toc: α -tocopherol, Toc-amine: *N*-methyl- α -tocopheramine, PG: propyl gallate, HyT: hydroxytyrosol, no stab.: no stabilizer used


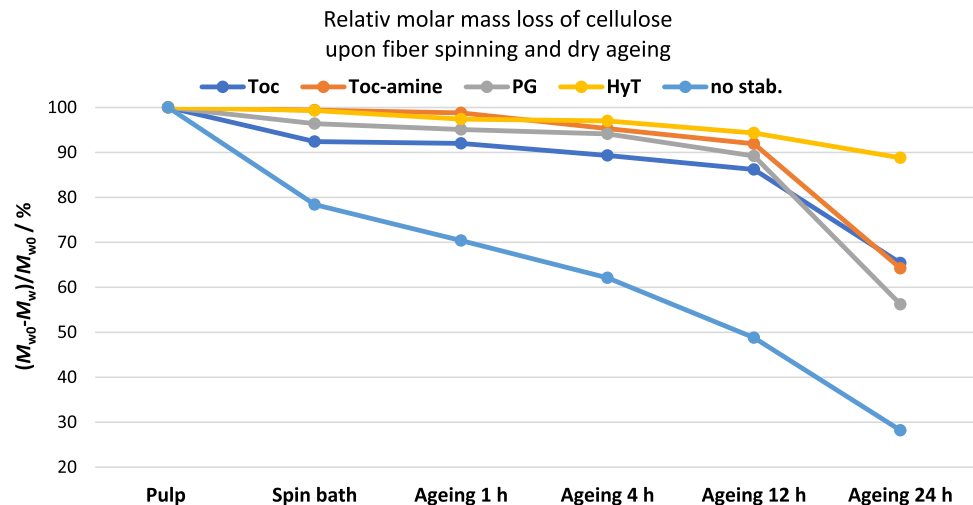


Fig. 2 Cellulose degradation (as molar mass loss relative to the starting pulp) upon spinning dope preparation and moist aging over different times. Toc: α -tocopherol, Toc-amine: *N*-methyl- α -tocopheramine, PG: propyl gallate, HyT: hydroxytyrosol, no stab.: no stabilizer used

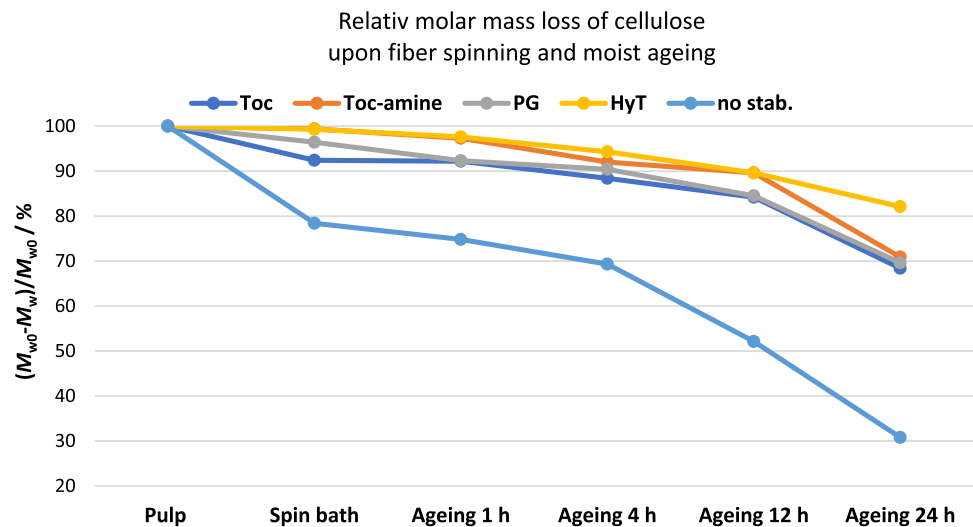

molar mass of the pulp: $(M_{w0}-M_w)/M_{w0}$ [%], with M_w being the determined molar mass and M_{w0} being the starting molar mass of the pulp.

The changes in ISO brightness with ageing are currently being investigated in detail. Suffice it to say that after 12 h of ageing, a brightness loss of approx. 5–6 ISO points was observed for all stabilizers, which corresponds approximately to the value for a non-stabilized fiber. While in this non-stabilized fiber, the chromophores are formed directly as a result of the oxidation of the polysaccharide components and subsequent condensation reactions [13], the chromophores in stabilized fibers are almost exclusively degradation products of the stabilizers: after their extraction, the brightness value returned to that of the unaged fiber.


Extraction of stabilizers and their degradation/oxidation products

All stabilizers and their degradation products are strongly to moderately lipophilic compounds, which is particularly true for the tocopherol derivatives with their isoprenoid $C_{16}H_{33}$ side chains [14]. While extraction from the aqueous spinning bath was easily possible by liquid–liquid extraction into toluene (unpublished work), the degradation products in the spun and aged fibers are tightly embedded in the fiber structure and not accessible to extraction with apolar organic solvents. To increase accessibility, swelling of the fiber with a polar aprotic solvent would be required. Such swelling in *N,N*-dimethylacetamide is used, for instance, as pretreatment before the dissolution of cellulosic pulps for analytical purposes (gel permeation chromatography, see [12]), or swelling in DMSO in the case of particularly hard-to-dissolve cellulosic fibers [15]. However, it was questionable whether the degradation products would remain chemically unchanged in this process and whether the swelling agents would extract the apolar degradation products. The addition of an apolar

solvent would not help as it could increase solubility, but at the same time would re-collapse the swollen fibers. For this reason, we resorted to extraction by supercritical carbon dioxide [16, 17], which offered the best solubility for the apolar substances and superb accessibility through the bulk of the fibers due to the extremely high diffusivity of the supercritical medium. In addition, the extract did not need any purification, drying, or evaporation treatments.

The extracts from the fibers (after 12 h of ageing) were screened by HP-TLC and GC–MS against a library of standard derivatives and oxidation products of the antioxidants used, which has resulted from previous work on antioxidants and has been expanded over the years to cover the common stabilizers used in cellulosic materials. Subsequent flash chromatography of the mixtures (toluene/*n*-heptane on silica gel) provided the separated major components. Extraction of the freshly spun fibers, for comparison, showed that approx. 70% of unchanged antioxidants were present. This agrees perfectly well with the values determined previously for the spinning dopes, which contained also about 70% of the antioxidants and only 30% of oxidation products. By contrast, after the fiber ageing, the antioxidants were almost completely converted into their oxidation products in the case of the tocopherol derivatives and propyl gallate, with the amount of unchanged stabilizers being below 10% and without significant differences between wet and dry ageing (Fig. 3). For hydroxytyrosol, not only the conversion rate was generally much lower, but there was also a significant gap between dry and moist ageing (74% vs. 51% consumption, respectively). As the protective effect was roughly the same for all four stabilizers (see Figs. 1 and 2), it can be concluded that hydroxytyrosol would provide a significantly longer stabilization time than the other three antioxidants when applied in the same molar amount, or it could be applied in smaller amounts to reach the same stabilization duration. In general, the continuous consumption of the stabilizers upon ageing nicely demonstrates the action of the

Fig. 3 Conversion of the tested antioxidants into their oxidation products in the spinning bath and after dry or moist fiber ageing

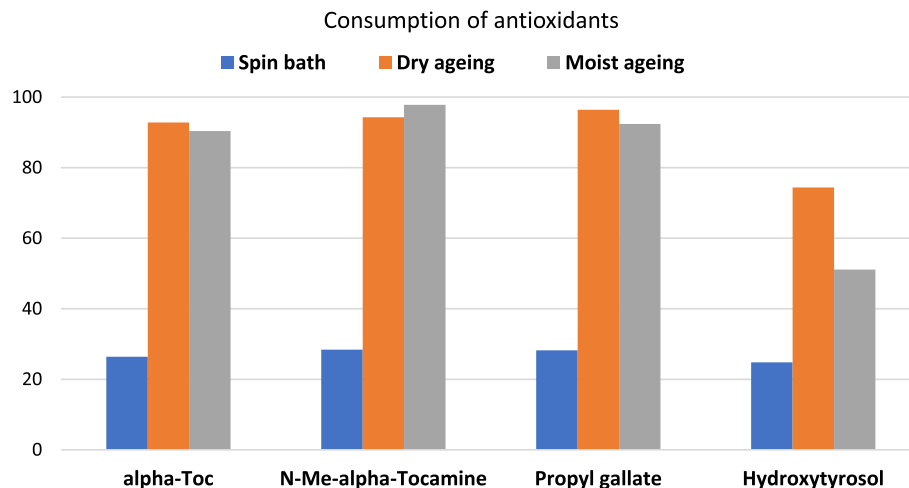

antioxidants in the fibers and mirrors the protective effect on cellulose integrity as discussed above.

Identification of the isolated chromophores and degradation/oxidation products

All identified chromophoric reaction products were analytically characterized by their NMR spectra, MS data, and the comparison to authentic samples, which were either available from previous work or independently synthesized. The identified compounds cover more than 95 wt% of the isolated reaction products for all four antioxidants used. The residual 5 wt% of minor side products (data not given here) cannot be considered as unambiguously identified as their amount was too low for comprehensive NMR analysis, although HP-TLC and MS data provided some indication as to their identity in almost all cases.

α -Tocopherol (**1**) is the main component of vitamin E, a mixture of tocopherols that are distinguished by different methylation patterns at the aromatic ring, with α -tocopherol—as the permethylated derivative—being the major component. It is the most common lipophilic antioxidant in vivo and most widely used in the food, feed, and cosmetics industries as additive E 307 [18]. But also in polymer and material science, it has found many usages as a stabilizer, antioxidant, and scavenger of radicals and reactive oxygen species, both in synthetic and renewable polymers and fibers [19–22]. Upon fiber ageing, α -tocopherol was converted into three major products, *para*-tocopherylquinone (**5**) [23, 24], the *spiro*-dimer of α -tocopherol (**6**) [25, 26], and the 5,6-*ortho*-quinone, so-called “ α -tocored” (**7**) [27]. The two former compounds are intensively yellow waxes in pure form, while the latter—as the name indicates—has a dark red color. It is responsible for the faint red hue of fibers stabilized with α -tocopherol. Compounds **5** and **6** are the typical reaction products of α -tocopherol, the *para*-quinone is the end product of oxidation in the presence of water, and the *spiro*-dimer is an almost ubiquitous reaction product of **1** which is formed by dimerization of the α -tocopherol-derived *ortho*-quinone methide (**1a**) [28, 29] in a hetero-Diels–Alder process with inverse electron demand. Intermediate **1a** is a central compound in the reactions of vitamin E with a rich chemistry. The selective involvement of the 5a-methyl group in *ortho*-quinone methide formation (while the other *ortho*-methyl group is rather unreactive) is a peculiarity of α -tocopherol which has been early recognized and accounted for by the theory of strain-induced bond localization [29, 30].


While *para*-quinone and *spiro*-dimer were also found in the spinning dope, α -tocored (**7**) was not: it was only present in the aged fibers and evidently formed only later upon ageing. It can thus well be used as an indicator for long-term ageing/storage of such tocopherol-stabilized fibers. A minor

antioxidant-derived component (2%) isolated from the fibers was *N*-(5a- α -tocopheryl)imidazole (**8**) which was formed by the addition of the *ortho*-quinone methide to traces of imidazole present. Imidazole and 1-methylimidazole are almost ubiquitous byproducts in imidazolium ionic liquids and the cellulose processed from them [31]. The reaction of the *ortho*-quinone methide with nucleophiles is a common reaction path in vitamin E chemistry, although the resulting 5a-substituted tocopherols are rather synthesized by reaction of the readily accessible 5a-bromo- α -tocopherol with the respective nucleophilic co-reactants [32]. Interestingly, *para*-quinone **5** can form the *ortho*-quinone methide **1a** by cyclization of an 8a-hydroxy- α -tocopherone (**5a**) derivative which undergoes a [1,4]-elimination of water, a reaction that has been frequently exploited in tocopherol chemistry. In the present case of fiber ageing, the reaction is responsible for the fact that upon dry ageing, *spiro*-dimer **6** dominated over the *para*-quinone **5** (72% vs. 8%) while in moist ageing the *para*-quinone was the dominant oxidation product (52% vs. 32%). The amount of α -tocored was 16% under both conditions and thus moisture-independent.

Scheme 2 shows the oxidation products (**5–8**) from the antioxidant α -tocopherol (**1**) in the aged fibers, spun from EMIm-OAc, and indicates their interrelation and conversions. Note that all oxidation products found are naturally occurring metabolites of α -tocopherol with well-known biocompatibility.

N-Methyl- α -tocopheramine (**2**) is a chemical sibling of α -tocopherol in which the phenolic OH group is replaced by an *N*-methyl moiety. As in the group of tocopherols, the α -homolog, i.e., the compound permethylated at the aromatic ring, is the most common representative also among the tocopheramines [33, 34]. Both tocopherols and tocopheramines are fully biocompatible and non-toxic [35] and excellent antioxidants [14] with wide applications in food and feed [36, 37], polymer technology [38, 39], and in the biomedical field [40–45]. *N*-Methyl- α -tocopheramine is obtained by demethylation of the *N,N*-dimethyl derivative [46] rather than by methylation of the parent compound α -tocopheramine, which always provides a hard-to-separate product mixture. In the cellulosic fibers stabilized with **2**, three reaction products were found, with *para*- α -tocopheryl quinone (**5**) as the main component. It is formed by oxidation of **2** to the corresponding *para*-iminoquinone, which immediately reacts with moisture under the formation of *para*- α -tocopheryl quinone (**5**) and release of methylamine. The second main product upon ageing under dry conditions was the *spiro*-dimer of *N*-methyl- α -tocopheramine (**9**), accompanied by small amounts of the *spiro*-dimer of α -tocopherol (**6**), in a molar ratio (**9/6**) of approx. 4.5:1, determined by weight. Upon ageing under moist conditions, this situation reversed, and **6** became by far dominant over **9**, with a ratio (**9/6**) of approx. 1:12. This demonstrates that the *spiro*-dimer

Scheme 2

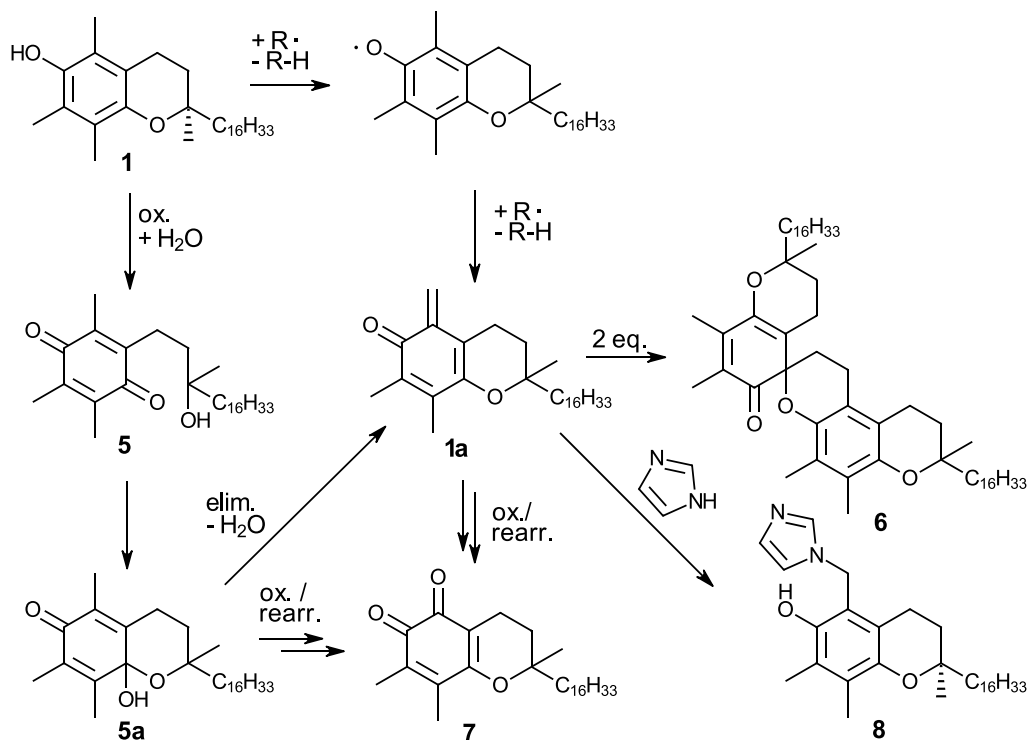

of *N*-methyl- α -tocopheramine (**9**), once formed by dimerization of the iminoquinone methide intermediate (**2a**) by analogy to the α -tocopherol case, is not stable, but loses methylamine in the presence of moisture, being converted to the *spiro*-dimer of α -tocopherol. Note that both *spiro*-dimers possess a fluxational nature with the aromatic part and the *spiro*-keto part changing their positions, as demonstrated by Netscher [26]. This explains why both nitrogen functionalities in **9** are replaced by the equivalent oxygen functionality in the reaction with water, and not only the more accessible *N*-methylamino moiety.


Interestingly, while α -tocopherol was contained in the spinning dopes stabilized with **2**, it was not found in the corresponding aged fibers, and thus was not newly formed from residual **2** upon accelerated ageing. This is a major difference to the α -tocopherol case. The absence of *N*-(5a- α -tocopheryl)imidazole (**8**) and other 5a-substituted tocopherol derivatives is in accordance with vitamin E chemistry, as the quinone methide intermediate **1a** easily adds nucleophiles to give 5a-substituted α -tocopherols, while the iminoquinone counterpart **2a** does not undergo such processes.

The reason for the use of the *N*-methyl derivative **2** as the stabilizer—instead of the non-methylated parent compound α -tocopheramine—is its well-defined oxidation chemistry, which avoids dark colored compounds and affords only innocuous products that are known as natural vitamin E metabolites. The reaction of the unmethylated

tocopheramine, by contrast, leads to the intensively red-colored azo-tocopherol as the main oxidation product [47], besides minor amounts of the potentially toxic nitrophenol 5-deoxy-5-nitro- α -tocopherol [48]. The *N,N*-dimethyl derivative has a significantly lower stabilizing effect as an antioxidant and has therefore not been used as a fiber stabilizer. The oxidation products from the antioxidant *N*-methyl- α -tocopheramine (**2**), compounds **5**, **6** (Scheme 3), are naturally occurring metabolites of α -tocopherol and are known to be non-toxic.

Propyl gallate (PG, **3**) is very commonly employed as a stabilizer and antioxidant: in food and cosmetic preparations as additive E 310, but also for polymeric materials and fibers [49–51]. It is also used, for instance, as a stabilizer in the production of cellulose Lyocell fibers in the solvent *N*-methylmorpholine *N*-oxide [39]. The aged fibers from dopes stabilized with propyl gallate contained mainly ellagic acid (**11**), a yellow crystalline compound in pure form, and its bis(*ortho*-quinone) **12**, a black amorphous solid. Both are the typical oxidation products of gallic acid and its esters. The primary phenoxyl radical intermediates formed from PG in its antioxidative action, recombine to intermediate 3,3',4,4',5,5'-hexahydroxydiphenic acid dipropyl ester (**3a**), which immediately affords ellagic acid (**11**) by bislactone formation. This cyclization is entropically driven and proceeds under the release of *n*-propanol from the ester moieties. The bis(*ortho*-quinone) **12**, with its

Scheme 3

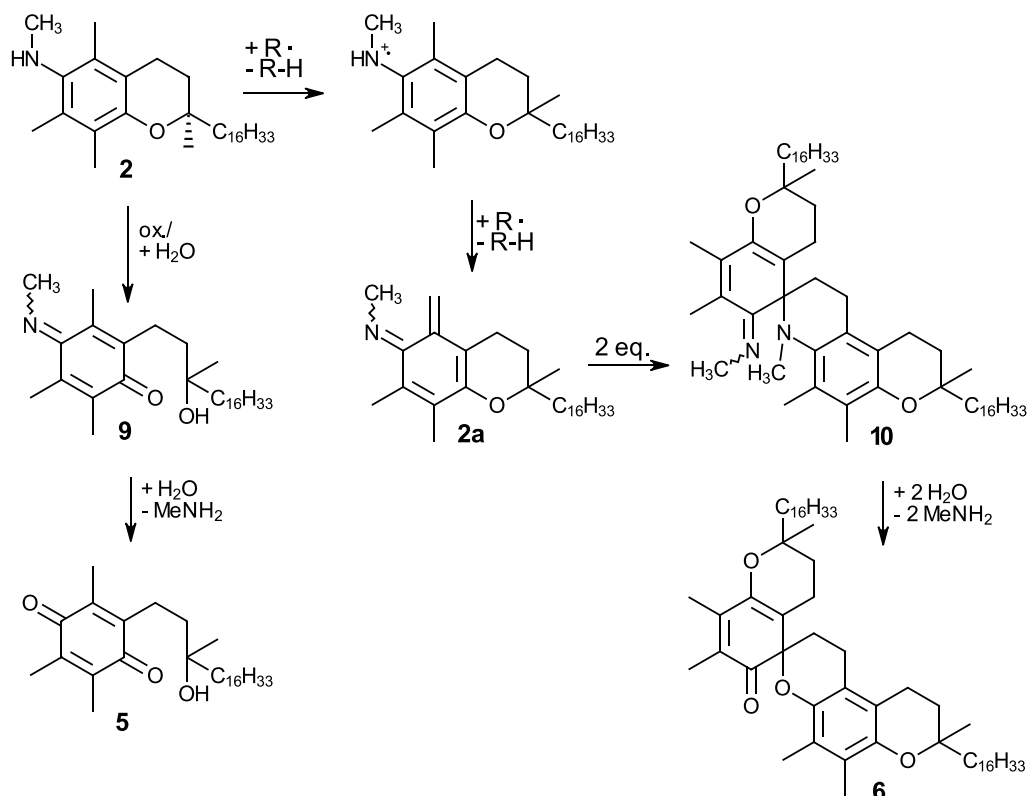

intensive blue-to-black color due to the highly conjugated double bond system, is chiefly responsible for the rather pronounced brightness loss of PG-stabilized fibers upon ageing.


While in the spinning dope free gallic acid was found, no gallic acid was present in the spun and aged fibers. Instead, gallic acid imidazole (**13**) was found as a minor component (3%). Formation of this compound cannot involve residual gallic acid, because amide formation from free acids would not occur, but would rather proceed as aminolysis of ester **3**. As mentioned above, imidazole, as the co-reacting amine component, is a common trace impurity when cellulose is processed in imidazolium ionic liquids. Scheme 4 summarizes the byproducts formed upon the ageing of PG-stabilized cellulosic fibers spun from the EMIm-OAc imidazolium ionic liquid.

Hydroxytyrosol (**4**) is a main antioxidant component in olive oil and olive leaf extract and is known for its beneficial nutraceutical effects [52, 53]. Its abundant occurrence in olive mill wastewater (OMWW) has promoted also non-food applications as a stabilizer for polymers [54, 55] and fibers [56, 57]. From EMIm-OAc-spun and subsequently aged fibers, the reaction products shown in Scheme 5 have been isolated. The yellow-orange *ortho*-quinone (**14**) is the primary product of both homolytic and heterolytic oxidation. While it was the dominant reaction product in the spinning


dope (short time, lower conversion), it was a minor component among the degradation products formed upon ageing (longer time, high conversion). Its intramolecular Michael addition product (**14a**), also found in the spinning dope, was not detected after ageing. Instead, a mixture of oxidation products with roughly equal concentrations was found (**15**, **16**, **16a**, **17**, **18**). Their formation pathways and interconversions will be discussed in detail in an upcoming account. Scheme 5 presents their structure and a brief formation mechanism summary.

ortho-Quinone **14** is a tautomer of *para*-quinone methide **14b**; such *ortho*-quinone/*para*-quinone (methide) tautomerization are very well-known, for instance, in lignin [58–60] or vitamin E chemistry [14, 29]. The *para*-quinone methide immediately adds a nucleophile—most commonly water/ OH^- —to form a benzyl alcohol derivative under rearomatization, which is also the thermodynamic driving force for the process. The resulting 1,2-dihydroxytyrosol (**15**), like its parent compound hydroxytyrosol (**4**), is a strong antioxidant and further oxidized to the corresponding *ortho*-quinone **16**. Similar to the *ortho*-quinone **14**, which affords **14a**, also *ortho*-quinone **16** undergoes intramolecular Michael addition to the bicyclic compound **16a** which, in turn, undergoes elimination of water in the furan ring and rearomatization in the benzene moiety. The lack of other intermediates

Scheme 4

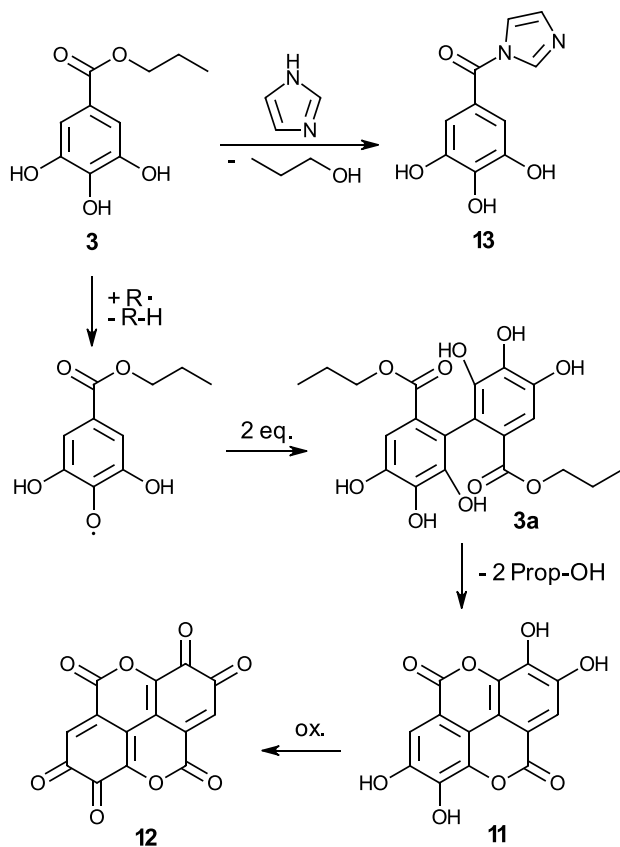

Scheme 5

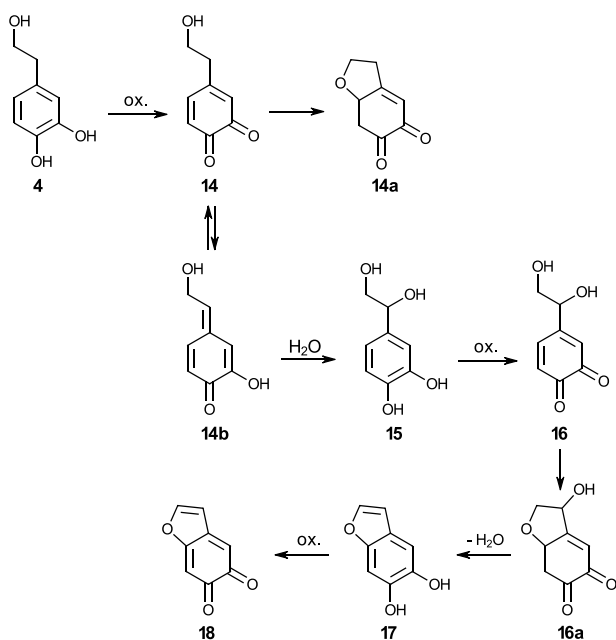

(compounds in which either water elimination or rearomatization had occurred, but not both at the same time) seems to indicate that both processes proceed simultaneously. The rearomatization process involves two tautomeric rearrangements, a keto-enol tautomerism ($4\text{-C}=\text{O}$) and a [1,5]-sigmatropic proton shift ($3\text{-C}=\text{O}$). The resulting dihydroxybenzofuran **17** was the major component found in the mixture of isolated oxidation products. The final product appears to be *ortho*-quinone **18**, which is obtained by further oxidation of **17**. Note that one molecule of hydroxytyrosol (**4**) is able to consume 6 one-electron oxidation-equivalents on the way to being eventually converted into *ortho*-quinone **18**. This explains its high antioxidative activity and also its high effectiveness as a stabilizer in the studied fibers.

TLC screening indicated that the formation of the Michael addition products found (**14a**, **16a**) was not an artifact of the work-up and isolation procedure, with increasing amounts being formed upon ageing. In both cases, the reaction could be reversed by dissolution in trifluoroacetic acid to generate the corresponding monocyclic *ortho*-quinones **14** and **16**.

Comparison of the degradation product mixtures from spinning dope, dry-aged and moist-aged fibers

The composition of the mixtures of degradation products from the stabilizers shows some significant differences when comparing the chromophores in the spinning dope on one side and those in the aged fibers on the other side. By contrast, the differences between moist and dry ageing are only minor – they can be traced back to reaction steps in which water is directly involved. Table 1 summarizes the differences in the mixtures of degradation products according to a simple system that classifies the degradation products as major product (>50%, + + +), product (+ +), and minor component (<5%, +). In this way, also the mechanistic differences, as discussed above, are visualized.

Important differences are the occurrence of α -tocored (**7**) in the aged fibers stabilized with α -tocopherol, but not in the corresponding spinning dope, while for the stabilizers *N*-methyl- α -tocopheramine the situation is reversed: α -tocored was found only in the dope, but not in the fibers. For both tocopherol-stabilizers, moist ageing conditions favor the formation of the *para*- α -tocopherylquinone (**5**) over the *spiro*-dimers (**6**, **10**) which is understandable from the formation mechanism. Oxidation to the *para*-quinone involves water, the formation of the *spiro*-dimers does not. Formation of the *spiro*-dimer from -tocopherol (**6**) by hydrolysis of the *spiro*-dimer from the tocopheramine (**10**) is a hydrolytic process that proceeds faster under moist ageing conditions than under dry ones.

The formation of 5a-(1-imidazolyl)- α -tocopherol (**8**) and gallic imidazolide (**13**) occurs only in the fibers, and not in

Table 1 Occurrence and prominence of the stabilizer-derived chromophores and degradation products (5–18) depending on spinning dope, dry-aged and moist-aged fibers

Chromophore / degradation product (cf. Schemes 2, 3, 4 and 5)	Spinning dope	Spun fiber, dry-aged	Spun fiber, moist-aged
From α-tocopherol (1)			
<i>para</i> - α -Tocopherylquinone (5)	++	++	++
α -Tocopherol <i>spiro</i> -dimer (6)	++	+++	++
α -Tocored (7)	–	++	++
5a-(1-Imidazolyl)- α -tocopherol (8)	–	+	+
From <i>N</i>-methyl-α-tocopheramine (2)			
<i>para</i> - α -Tocopherylquinone (5)	++	+++	+++
α -Tocopherol <i>spiro</i> -dimer (6)	+	+	++
α -Tocopherylamine <i>spiro</i> -dimer (10)	+	++	+
α -Tocored (7)	++	–	–
From propyl gallate (3)			
Ellagic acid (11)	++	+++	+++
Ellagic acid bis(<i>ortho</i> -quinone) (12)	++	++	++
Gallic imidazolide (13)	–	+	+
From hydroxytyrosol (4)			
Hydroxytyrosol <i>ortho</i> -quinone (14)	+++	+	+
Dihydroxytyrosol (15)	–	+	+
Dihydroxytyrosol <i>ortho</i> -quinone (16)	–	++	++
5,6-Dihydroxybenzofuran (17)	–	+	++
<i>ortho</i> -Quinone 18	–	++	++

the spinning dope. Both involve not only stabilizer-derived precursors but also imidazole as a degradation product of the ionic liquid. In the case of the stabilizer hydroxytyrosol (4), only the first oxidation product, *ortho*-quinone 14, is found in the spinning dope. In the fibers, both stabilizer and 14 are largely depleted by further transformation into more highly oxidized products (16–18), of which 18 seems to be the final product that is stable and not further modified.

Conclusions

In this study, we have investigated the formation of oxidation / degradation products from stabilizers in cellulosic fibers spun from the EMIM-OAc ionic liquid. All stabilizers were natural antioxidants, namely α -tocopherol, *N*-methyl- α -tocopheramine, propyl gallate, and hydroxytyrosol. While these antioxidants effectively protect against cellulose degradation during dope preparation, fiber spinning and fiber shelf-life, a trade-off emerges in the form of chromophore generation, leading to discoloration of the spinning dope and resulting fibers. The antioxidants' protective effects were demonstrated by comparing the cellulose molar mass of stabilized and non-stabilized fibers, revealing a significant retention of molar mass in the stabilized fibers, highlighting the effectiveness of the chosen antioxidants. The concomitant conversion to chromophores was seen as a noticeable brightness loss upon accelerated ageing.

The study addressed the identification of oxidation and degradation products of the four antioxidants formed upon accelerated ageing of the fibers under dry and moist conditions. It employed advanced techniques, such as supercritical carbon dioxide extraction, to isolate degradation products from the aged fibers, and NMR spectroscopy with comparison to authentic samples for final unambiguous identification. A total of 16 different oxidation/degradation products were isolated, analytically characterized, structurally identified, and their formation pathways discussed. The antioxidants exhibited varying degrees of degradation, and their consumption was influenced by both the type of antioxidant and the ageing conditions. α -Tocopherol and *N*-methyl- α -tocopheramine were largely consumed during ageing, leading to the formation of specific chromophores such as *para*-tocopherylquinone, *spiro*-dimers, and α -tocored. Propyl gallate, also largely consumed during ageing, resulted in the generation of ellagic acid and its bis(*ortho*-quinone), contributing to the observed discoloration. Hydroxytyrosol, a prominent component in olives, exhibited a special effect: it formed a yellow-orange *ortho*-quinone as an initial oxidation product, which was further transformed into secondary products that were potential antioxidants as well. Its overall consumption rate was thus lower than in the case of the other three antioxidants. Interestingly, imidazole, as almost ubiquitous trace byproduct of the imidazolium ILs, was incorporated into the stabilizer degradation products in two cases.

The differences observed between the chromophores in the spinning dope and those in the aged fibers underscore the dynamic nature of antioxidant degradation during fiber processing and ageing. Moisture content during ageing influenced the distribution of certain chromophores, emphasizing the importance of considering environmental conditions in fiber stabilization processes (see Table 1).

The results provide valuable insights into the chemical structures of the chromophores generated during the ageing process. This knowledge serves as a crucial foundation for optimizing the fiber bleaching stage, addressing challenges related to brightness loss, chemical needs for bleaching treatments and brightness stability. Alternative antioxidants, which meet the principles of green chemistry but at the same time do not produce chromophoric reaction products upon their action, are evidently also an important direction of research. Future research will now focus on refining the stabilizer dosage, exploring alternative stabilization methods, and optimizing the bleaching process to enhance the commercial viability and sustainability of cellulosic fibers spun from 1,3-dialkylimidazolium ILs.

Experimental

All chemicals were of the highest purity available and used without further purification. Bidistilled water was used for all aqueous solutions, extractions, and washing steps. 1,4-Dioxane, *n*-heptane, ethyl acetate, and toluene used in chromatography were distilled before use. TLC was performed using Merck silica gel 60 F₂₅₄ pre-coated plates, and flash chromatography on Baker silica gel (40 µm particle size). All products were purified to homogeneity by TLC / GC analysis and satisfying elemental analysis data ($\pm 0.2\%$). Elemental analyses were performed at the Microanalytical Laboratory of the University of Vienna. The melting points are corrected (benzophenone 48–49 °C, benzoic acid 122–123 °C), determined on a Kofler-type micro hot stage with Reichert-Biovar microscope.

The same cellulosic pulp, having an α -cellulose contents of 97.5% according to the manufacturer, and fibers produced thereof was used as in previous work [6, 7], $M_n = 99.3$ kDa, $M_w = 362.7$ kDa, degree of polymerization (DP) = 2237, dispersity $\mathcal{D} = M_w/M_n = 3.65$, and ISO brightness = 82. The molar mass data were determined by size exclusion chromatography according to the published standard protocol [12]. The EMIm-OAc ionic liquid was obtained from Nippon Nyukazai Co., Ltd. (Tokyo, Japan).

Gel permeation chromatography (size exclusion chromatography) was used applying the standard protocol according to Potthast et al. [12], where also the SEC-MALS system is described in detail. In short, DMAc-activated samples were placed in 4 cm³ vials, and an *N,N*-dimethylacetamide

(DMAc)/lithium chloride solution (1 cm³, 9% w/v) was added to each sample. The vials were vortexed for 20 s and placed in a rotary shaker again for over 20 h to dissolve the samples, then the samples were diluted 1:3 (v/v) with pure DMAc and filtered through PTFE syringe filters (0.45 µm) before SEC-MALS analysis. The calculations were based on a refractive index increment for cellulose of 0.136 cm³ g⁻¹. Viscometry measurements used the solvent cupriethylene diamine (cuen) according to a previously published, improved protocol [61], which avoids systematic underestimation errors due to β -elimination reactions [62].

GC-MS/FID and UPC²-ESI-QToF-MS analysis were performed as previously described by Barbini et al. [16, 17]. UV/Vis spectra were recorded on a LAMBDA 45 UV/Vis spectrophotometer (Perkin Elmer, Waltham, MA, USA): range of 400 to 700 nm, scanning speed 480 nm min⁻¹, quartz glass cuvettes (l = 1.0 cm).

Preparation of spinning dopes and dry-jet wet spinning

The cellulosic pulps were dried at 100 °C for 3 h. In a stainless-steel vessel, a pulp aliquot (5 wt% rel. to the IL solvent) was added to 1-ethyl-3-methylimidazolium acetate ionic liquid containing the stabilizer (2 wt% rel. to the mass of cellulosic pulp) and stirred at room temperature for 1 h. The mass of added stabilizer corresponds to 0.76 mol% for α -tocopherol (**1**), 0.74 mol% for *N*-methyl- α -tocopheramine (**2**), 1.56 mol% for propyl gallate (**3**), and 2.15 mol% for hydroxytyrosol (**4**), relative to cellulose (molar mass of the glucopyranose unit: 162.135 g mol⁻¹). The mixture was heated to 100–130 °C under stirring to affect the dissolution of the pulp. Complete dissolution, occurring after an additional 1–2 h, was confirmed using a polarized optical microscope (Olympus BHT-P, Tokyo, Japan) under crossed Nicols.

Spinning was carried out according to a dry-jet wet spinning process as reported previously [6, 7, 10]. At a temperature of 100 °C, the spinning dopes were extruded through the spinning nozzles into an air gap (15 cm) and distilled water (without any additives) as the coagulation bath, at a constant throughput speed of 0.1 cm³ min⁻¹ and a constant winding speed of 107 m min⁻¹. The resulting fibers were washed with hot distilled water (70 °C) to remove the major part of the solvent and byproducts, loosely coiled on bobbins, agitated in water overnight to remove residues of solvent and byproducts, and dried at room temperature.

Accelerated ageing of the fibers

Hand sheets were prepared from 2 g of fibers suspended in distilled water (500 cm³) on a Büchner funnel, followed by pressing and drying at 92 °C for 5 min. Brightness was

measured before and after ageing according to ISO 2470 (2009) [63], detecting UV/Vis remission at 457 nm. Continuous ageing was performed either under dry conditions according to the TAPPI method UM 200 (105 °C, 40% rel. humidity, 4 h, 12 h, 24 h) [64] or under humid conditions according to Paptac E.4P (100 °C, 100% rel. humidity, 4 h, 12 h, 24 h) [65]. The ageing progress was monitored by UV/Vis (brightness reversion) to follow the kinetics of chromophore generation.

Extraction of stabilizer-derived degradation products and chromophores from the spinning baths by supercritical CO₂

Supercritical extraction of the aged fibers was carried out with carbon dioxide (>99.5% food grade, Biogon C, Linde AG, Austria) on a high-pressure SF-1 supercritical fluid system (Separex, Champigneulle, France) equipped with preheater, autoclave, and separator. Aliquots of the fibers (approx. 25 g) were extracted for 90 min at a flow rate of 30 g min⁻¹, and the extracts were combined. Extraction proceeded at 30 MPa (300 bar) and 40 °C (ρ CO₂: 910 kg m⁻³) in a cylindrical extraction vessel (diameter: 35 mm, height: 50 mm). In the case of propyl gallate-stabilized fibers, 1 wt% of ethanol 96 vol% ($\rho_{20^\circ\text{C}}$: 808.5 kg m⁻³, Merck) was added as a co-solvent by an HPLC pump (Lab Alliance) to enhance the solubility of ellagic acid (**11**) and its bis(*ortho*-quinone) (**12**). The extracts were stored under argon gas at -20 °C in brown-glass vials.

NMR analysis and identification of chromophores

All NMR spectra were recorded on a Bruker Avance II 400 (resonance frequencies 400.13 MHz for ¹H and 100.63 MHz for ¹³C) equipped with a 5 mm N₂-cooled cryoprobe head (Prodigy) with z-gradients at room temperature with standard Bruker pulse programs. The sample was dissolved in 0.6 cm³ of CDCl₃ (99.9% D). Chemical shifts are given in ppm, referenced to residual solvent signals. ¹H NMR data were collected with 32 k complex data points and apodized with a Gaussian window function (lb = -0.3 Hz and gb = 0.3 Hz) prior to Fourier transformation. ¹³C spectrum with WALTZ16 ¹H decoupling was acquired using 64 k data points. Signal-to-noise enhancement was achieved by multiplication of the FID with an exponential window function (lb = 1 Hz). All two-dimensional experiments were performed with 1 k × 256 data points, while the number of transients (2–16 scans) and the sweep widths were optimized individually. HSQC experiment was acquired using adiabatic pulse for inversion of ¹³C and GARP-sequence for broadband ¹³C-decoupling, optimized for ¹J_(CH) = 145 Hz. For the NOESY spectra, a mixing time of 0.8 s was used.

The nomenclature and atom numbering of tocopherols and chromanols as recommended by IUPAC was used throughout [66, 67]. ¹H and ¹³C NMR resonances of the isoprenoid side chain of tocopherols are only insignificantly influenced ($\Delta < 0.05$ ppm) by modifications of the chroman ring [68, 69], and are thus listed here only once: $\delta = 19.7$ (C-4a'), 19.8 (C-8a'), 21.2 (C-2'), 22.7 (C-13'), 22.8 (C-12a'), 24.6 (C-6'), 24.8 (C-10'), 28.0 (C-12'), 32.6 (C-8'), 32.8 (C-4'), 37.3 (C-7'), 37.4 (C-9'), 37.5 (C-5'), 37.5 (C-3'), 39.3 (C-11'), 39.9 (C-1') ppm. In the *spiro*-dimeric compounds **6** and **10**, the aromatic moiety is conventionally numbered, while the *spiro*-keto moiety is indicated by "#".

para- α -Tocopherylquinone (5) Dark yellow oil; UV (toluene): $\lambda_{\text{max}} = 264$ nm; ¹H NMR: $\delta = 2.55$ (2H, m, 4-CH₂), 2.08 (3H, s, 5a-CH₃), 2.03 (3H, s, 7a-CH₃), 2.03 (3H, s, 8b-CH₃), 1.08–1.54 (m, 23H, 3-CH₂, 9 × CH₂ in side chain [1'-CH₂, 2'-CH₂, 3'-CH₂, 5'-CH₂, 6'-CH₂, 7'-CH₂, 9'-CH₂, 10'-CH₂, 11'-CH₂], 3 × CH in side chain [4-CH, 8-CH, 12-CH]), 1.23 (3H, s, 2a-CH₃), 0.86 (9H, d, $J = 6.3$ Hz, 4a-CH₃, 8a-CH₃, 12a-CH₃), 0.84 (3H, d, $J = 6.3$ Hz, 13-CH₃) ppm; ¹³C: $\delta = 187.5$ (C-8a), 140.3 (C-8), 12.3 (C-8b), 140.0 (C-7), 12.3 (C-7a), 186.6 (C-6), 140.6 (C-5), 12.0 (C-5a), 144.4 (C-4a), 21.5 (C-4), 40.4 (C-3), 72.7 (C-2), 26.7 (C-2a) ppm; isoprenoid side chain: see above. NMR data fully agree with the literature [25, 70].

Spiro-dimer of α -tocopherol (6) Yellow oil; UV (toluene): $\lambda_{\text{max}} = 272$ nm; ¹H NMR: $\delta = 2.62$ (2H, m, 4-CH₂), 2.46 (2H, m, 4#-CH₂), 2.52 (3H, s, 5a-CH₂), 2.08 (3H, s, 5a#-CH₂), 2.12 (3H, s, 7a-CH₃), 1.88 (3H, s, 7a#-CH₃), 2.05 (3H, s, 8b-CH₃), 2.01 (3H, s, 8b#-CH₃), 1.64–1.60 (4H, m, 3-CH₂ and 3#-CH₂), 1.06–1.54 (m, 42H, 18 × CH₂ and 6 × CH in two isoprenoid side chains), 1.22 (3H, s, 2a-CH₃), 1.20 (3H, s, 2a#-CH₃), 0.82–0.90 (24H, m, 4a-CH₃, 8a-CH₃, 12a-CH₃, 13-CH₃, 4a#-CH₃, 8a#-CH₃, 12a#-CH₃, 13#-CH₃) ppm; ¹³C NMR: $\delta = 143.7$ (C-8a), 141.8 (C-8a#), 122.4 (C-8, C-8#), 10.7 (C-8b), 13.0 (C-8b#), 121.1 (C-7), 126.0 (C-7#), 10.8 (C-7a), 10.2 (C-7a#), 144.7 (C-6), 201.4 (C-6#), 114.5 (C-5), 80.0 (C-5#), 16.9 (C-5a), 27.1 (C-5a), 114.0 (C-4a), 114.4 (C-4a#), 18.6 (C-4), 16.6 (C-4#), 29.7 (C-3), 30.2 (C-3#), 73.3 (C-2), 75.0 (C-2), 22.3 (C-2a), 22.5 (C-2a#) ppm; isoprenoid side chains: see above. NMR data are in complete agreement with the literature [26].

α -Tocopheryl-*ortho*-quinone (α -tocored, 7) Red oil; UV (toluene): $\lambda_{\text{max}} = 288$ nm; ¹H NMR: $\delta = 2.44$ (2H, m, 4-CH₂), 2.05 (3H, s, 7a-CH₃), 1.98 (3H, s, 8b-CH₃), 1.73 (2H, t, 3-CH₂), 1.08–1.54 (m, 21H, 9 × CH₂ in side chain [1'-CH₂, 2'-CH₂, 3'-CH₂, 5'-CH₂, 6'-CH₂, 7'-CH₂, 9'-CH₂, 10'-CH₂, 11'-CH₂], 3 × CH in side chain [4-CH, 8-CH, 12-CH]), 1.28 (3H, s, 2a-CH₃), 0.84–0.86 (12H, d, $J = 6.3$ Hz, 4a-CH₃, 8a-CH₃, 12a-CH₃), 0.84 (3H, d, $J = 6.3$ Hz, 13-CH₃) ppm;

^{13}C NMR: $\delta = 163.5$ (C-8a), 110.3 (C-8), 11.7 (C-8b), 134.4 (C-7), 13.8 (C-7a), 180.1 (C-6), 181.0 (C-5), 143.8 (C-4a), 22.6 (C-4), 40.0 (C-3), 71.4 (C-2), 28.0 (C-2a) ppm; isoprenoid side chain: see above. NMR data are fully consistent with the literature [71].

5a-(1-Imidazolyl)- α -tocopherol (8) ^1H NMR: $\delta = 2.11$ (3H, s, 7a- CH_3), 2.15 (3H, s, 8b- CH_3), 2.60 (2H, t, 4- CH_2), 3.85 (2H, s, 5a- CH_2), 6.83 (s, 1H, H(Im)-5); 7.02 (s, 1H, H(Im)-4), 7.40 (s, 1H, H(Im)-2) ppm; ^{13}C NMR: $\delta = 11.7$ (C-8b), 11.9 (C-7a), 19.4 (C-4), 31.1 (C-3), 51.4 (C-5a), 74.5 (C-2), 114.2 (C-4a), 115.7 (C-5), 124.0 (C-7), 125.3 (C-8), 128.1 (C(Im)-4), 129.3 (C(Im)-5), 138.4 (C(Im)-2), 144.5 (C-8a), 145.7 (C-6) ppm.

Spiro-dimer of N-methyl- α -tocopheramine (10) Yellow oil; UV (toluene): $\lambda_{\text{max}} = 278$ nm; ^1H NMR: $\delta = 2.60$ (2H, m, 4- CH_2), 2.46 (2H, m, 4#- CH_2), 2.36 (3H, s, 5a- CH_3), 2.18 (3H, s, 5a#- CH_3), 2.05 (3H, s, 7a- CH_3), 1.84 (3H, s, 7a#- CH_3), 2.01 (3H, s, 8b- CH_3), 1.96 (3H, s, 8b#- CH_3), 1.64–1.59 (4H, m, 3- CH_2 and 3#- CH_2), 1.06–1.54 (m, 42H, 18 \times CH_2 and 6 \times CH in two isoprenoid side chains), 1.22 (3H, s, 2a- CH_3), 1.21 (3H, s, 2a#- CH_3), 0.82–0.92 (24H, m, 4a- CH_3 , 8a- CH_3 , 12a- CH_3 , 13- CH_3 , 4a#- CH_3 , 8a#- CH_3 , 12a#- CH_3 , 13#- CH_3) ppm; ^{13}C NMR: $\delta = 145.4$ (C-8a), 142.4 (C-8a#), 122.8 (C-8), 122.6 (C-8#), 10.7 (C-8b), 12.9 (C-8b#), 123.2 (C-7), 125.8 (C-7#), 10.9 (C-7a), 10.4 (C-7a#), 138.6 (C-6), 251.3 (C-6#), 111.2 (C-5), 68.7 (C-5#), 18.8 (C-5a), 25.5 (C-5a), 116.2 (C-4a), 116.0 (C-4a#), 18.8 (C-4), 16.6 (C-4#), 30.2 (C-3, C-3#), 73.8 (C-2), 75.1 (C-2), 22.3 (C-2a, C-2a#), 38.8 (CH₃-N), 42.4 (CH₃-N=) ppm; isoprenoid side chains: see above.

Ellagic acid (11) Yellow powder; ^1H NMR: $\delta = 7.46$ (H-Ar), 8.12 (OH) ppm; ^{13}C NMR: $\delta = 107.4$ (C-2), 110.2 (C-6), 112.4 (C-1), 136.3 (C-3), 140.1 (C-4), 148.1 (C-5), 159.1 (COO) ppm.

Ellagobis(ortho-quinone) (2,3,5,7,8,10-Hexahydrochromeno[5,4,3-cde]chromene-2,3,5,7,8,10-hexaone, 12) Black powder; ^1H NMR: $\delta = 8.05$ (CH) ppm; ^{13}C NMR: $\delta = 116.1$ (C-6), 115.9 (C-1), 118.8 (C-2), 145.0 (C-3), 155.9 (COO), 177.5 (C-4), 180.4 (C-5) ppm.

Gallic imidazolide (13) Yellow needles; ^1H NMR: $\delta = 6.32$ (s, 2H, 2-CH, 6-CH), 6.81 (s, 1H, H(Im)-5), 7.08 (s, 1H, H(Im)-4), 7.44 (s, 1H, H(Im)-2) ppm; ^{13}C NMR: $\delta = 107.9$ (C-2, C-6), 125.5 (C-1), 127.2 (C(Im)-4), 129.2 (C(Im)-5), 145.6 (C-3, C-5), 135.5 (C-4), 138.2 (C(Im)-2), 166.1 (CON) ppm.

Hydroxytyrosol ortho-quinone (14) Red oil; ^1H NMR: $\delta = 2.69$ (2H, t, Ar- CH_2), 3.70 (2H, t, CH_2 -OH), 6.60 (1H,

dd, H-6), 6.72 (1H, dd, H-2), 6.78 (1H, dd, H-5) ppm; ^{13}C NMR: $\delta = 31.2$ (Ar- CH_2) 61.4 (CH_2 -OH), 127.7 (CH-5), 129.2 (CH-2), 143.2 (CH-6), 151.1 (C-1), 180.3 (C-4), 182.4 (C-3) ppm.

Dihydroxytyrosol (15) Yellowish wax; ^1H NMR: $\delta = 3.42$ (2H, dd, $J = 3.6, 8.0$ Hz, Ar-CH(OH)), 4.04 (1H, dd, $J = 3.6, 8.0$ Hz, CH_2 -OH), 6.54 (1H, dd, $J = 2.0, 8.0$ Hz, H-6), 6.67 (1H, d, $J = 8.0$ Hz, H-5), 6.75 (1H, d, $J = 2.0$ Hz, H-2) ppm; ^{13}C NMR: $\delta = 66.5$ (CH_2 -OH), 84.9 (Ar-CH(OH)), 115.4 (CH-2), 116.1 (CH-5), 120.3 (CH-6), 131.1 (C-1), 143.6 (C-4), 144.9 (C-3) ppm.

Dihydroxytyrosol ortho-quinone (16) Red oil; ^1H NMR: $\delta = 3.44$ (2H, dd, $J = 3.6, 7.9$ Hz, Ar-CH(OH)), 3.99 (1H, dd, $J = 3.6, 7.9$ Hz, CH_2 -OH), 6.56 (1H, dd, H-6), 6.70 (1H, dd, H-2), 6.76 (1H, dd, H-5) ppm; ^{13}C NMR: $\delta = 66.1$ (CH_2 -OH), 85.2 (Ar-CH(OH)), 127.2 (CH-5), 128.8 (CH-2), 143.4 (CH-6), 151.9 (C-1), 182.4 (C-4), 185.5 (C-3) ppm.

5,6-Dihydroxybenzofuran (17) Yellow wax; ^1H NMR: $\delta = 5.23$ (2H, br, OH), 6.42 (1H, t, $J = 3.2$ Hz, H-2), 7.24 (1H, t, $J = 3.2$ Hz, H-3), 7.42 (1H, d, $J = 0.6$ Hz, H-4), 7.48 (1H, d, $J = 0.6$ Hz, H-7) ppm; ^{13}C NMR: $\delta = 106.1$ (CH-7), 106.9 (CH-3), 124.6 (CH-4), 127.9 (C-3a), 143.2 (CH-2), 144.2 (C-5), 150.1 (C-6), 155.4 (C-8) ppm.

5,6-Dihydroxybenzofuran ortho-quinone (18) Red oil; ^1H NMR: $\delta = 6.33$ (1H, t, $J = 3.2$ Hz, H-2), 6.88 (1H, t, $J = 3.2$ Hz, H-3), 7.02 (1H, s, H-4), 7.08 (1H, s, H-7) ppm; ^{13}C NMR: $\delta = 110.1$ (CH-3), 126.5 (CH-3a), 131.2 (C-4), 133.4 (CH-7), 145.1 (C-2), 150.1 (C-8), 182.3, 182.6 (C-5, C-6) ppm.

Acknowledgements The financial support of the Austrian Biorefinery Center Tulln (ABCT-II) is gratefully acknowledged. The county of Lower Austria is gratefully acknowledged for the support through the project WST3-F-5030820 (Stabilization of polymers through antioxidants).

Funding Open access funding provided by University of Natural Resources and Life Sciences Vienna (BOKU).

Data availability Complete analytical data are provided in the article.

Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will

need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

References

- Sixta H, Iakovlev M, Testova L, Roselli A, Hummel M, Borrega M, van Heiningen A, Froschauer C, Schottenberger H (2013) *Cellulose* 20:1547
- Sixta H, Michud A, Hauru L, Asaadi S, Ma Y, King AWT, Kilpeläinen I, Hummel M (2015) *Nord Pulp Paper Res J* 30:43
- Stepan AM, Michud A, Hellstén S, Hummel M, Sixta H (2016) *Ind Eng Chem Res* 55:8225
- Asaadi S, Kakko T, King AWT, Kilpeläinen I, Hummel M, Sixta H (2018) *ACS Sust Chem Eng* 6:9418
- Guizani C, Larkiala S, Moriam K, Sawada D, Elsayed S, Rantasalo S, Hummel M, Sixta H (2021) *J Appl Polym Sci* 138:49787
- Zhang J, Kitayama H, Potthast A, Rosenau T, Gotoh Y (2019) *Carbohydr Polym* 226:115258
- Zhang J, Yamagishi N, Gotoh Y, Potthast A, Rosenau T (2020) *J Appl Polym Sci* 137:48681
- Ebner G, Schiehser S, Potthast A, Rosenau T (2008) *Tetrahedron Lett* 49:7322
- Zweckmair T, Hettegger H, Abushamallah H, Bacher M, Potthast A, Laborie MP, Rosenau T (2015) *Cellulose* 22:3583
- Hettegger H, Zhang J, Koide M, Rinner U, Potthast A, Gotoh Y, Rosenau T (2022) *Fibers* 10:50
- Stolze K, Udilova N, Rosenau T, Hofinger A, Nohl H (2003) *Biol Chem* 384:457
- Potthast A, Rosenau T, Henniges U, Schiehser S, Kosma P, Saake B, Lebioda S, Radosta S, Vorwerg W, Wetzel H, Koschella A, Heinze T, Strobin G, Sixta H, Strlic M, Isogai A (2015) *Cellulose* 22:1591
- Korntner P, Hosoya T, Dietz T, Eibinger K, Reiter H, Spitzbart M, Röder T, Borgards A, Kreiner W, Mahler AK, Winter H, French AD, Henniges U, Potthast A, Rosenau T (2015) *Cellulose* 22:1053
- Preedy VR, Watson RR (eds) (2007) *Encyclopedia of Vitamin E*. CABI Publishing, Oxford, Cambridge
- Henniges U, Vejdovszky P, Siller M, Jeong MJ, Rosenau T, Potthast A (2014) *Curr Chromatogr* 1:52
- Barbini S, Jaxel J, Karlström K, Rosenau T, Potthast A (2021) *Bioresour Technol* 341:125862
- Barbini S, Sriranganadane D, España Orozco S, Kabrelian A, Karlström K, Rosenau T, Potthast A (2021) *ACS Sust Chem Eng* 9:1323
- Catala A (2012) *Tocopherol: sources, uses and health benefits*. Nova Science, UK
- Dahe GJ, Teotia RS, Kadam SS, Bellare JR (2011) *Biomaterials* 32:352
- Wu HL, Bremner DH, Li HY, Shi QQ, Wu JZ, Xiao RQ, Zhu LM (2016) *Mat Sci Eng C* 62:702
- Ghaheh FS, Khoddami A, Alihosseini F, Jing S, Ribeiro A, Cavaco-Paulo A, Silva C (2017) *Process Biochem* 59:46
- Yokota S, Kitaoka T, Opietnik M, Rosenau T, Wariishi H (2008) *Angew Chem Int Ed* 47:9866
- Rüegg R, Mayer H, Schudel P, Schwieter U, Tamm R, Isler O (1967) *Veröffentl Deut Ges Ernährung* 16:22
- Machlin LJ (1980) *Vitamin E: a comprehensive treatise*. Marcel Dekker, New York
- Schudel P, Mayer H, Metzger J, Rüegg R, Isler O (1963) *Helv Chim Acta* 46:636
- Schröder H, Netscher T (2001) *Magn Reson Chem* 39:701
- Rosenau T, Gruner M, Habicher WD (1997) *Tetrahedron* 53:3571
- Rosenau T, Potthast A, Elder T, Kosma P (2002) *Org Lett* 4:4285
- Rosenau T, Böhmendorfer S (2009) ortho-Quinone methides in tocopherol chemistry. In: Rokita S (ed), *Wiley series on reactive intermediates in chemistry and biology*, vol 1. Wiley, New York, p 163
- Rosenau T, Ebner G, Stanger A, Perl S, Nuri L (2005) *Chem Eur J* 11:280
- Liebner F, Ebner G, Becker E, Potthast A, Rosenau T (2010) *Holzforchung* 64:161
- Rosenau T, Habicher WD (1995) *Tetrahedron* 51:7919
- Smith LI, Renfrow WB, Opie JW (1942) *J Am Chem Soc* 64:1082
- Mayer H, Isler O (1971) Tocopheramines and tocopherthiols. In: Colowick SP, Kaplan NO (eds) *Methods in enzymology*, vol 18, part C. Academic Press, New York, London, p 275, 334
- Blomstrand R, Forsgren L (1968) *Int J Vit Res* 38:328
- Schlegel W, Schwieter U, Tamm R (1969) Non-toxic antioxidants, based on chromane derivatives. US Patent 3458637, Jul 29, 1969; (1968). *Chem Abstr* 69:21909
- Søndergaard E, Dam H (1970) *Zeitschr Ernährungswiss* 10:71
- Tokuwame M (1991) Synergistic antioxidant-heat stabilizer systems for polyolefins. JP Patent 03043458, Feb 25. *Chem Abstr* 115:73015
- Rosenau T, Potthast A, Milacher W, Adorjan I, Hofinger A, Kosma P (2005) *Cellulose* 12:197
- Tomic-Vatic A, Eytina J, Chapman J, Mahdavian E, Neuzil J, Salvatore BA (2005) *Int J Cancer* 117:188
- Gille L, Stamberg W, Patel A, Böhmendorfer S, Rosenau T (2012) *Free Rad Biol Med* 53:100
- Zingg JM (2007) *Mini Rev Med Chem* 7:545
- Neuzil J, Tomasetti M, Zhao Y, Dong LF, Birringer M, Wang XF, Low P, Wu K, Salvatore BA, Ralph SJ (2007) *Mol Pharmacol* 71:1185
- Tanito M, Yoshida Y, Kaidzu S, Chen ZH, Cynshi O, Jishage KI, Niki E, Ohira A (2007) *Investig Ophthalmol Visual Sci* 48:396
- Bieri JG, Mason KE (1968) *J Nutr* 96:192
- Rosenau T, Hofinger A, Potthast A, Kosma P (2004) *Org Lett* 6:541
- Patel A, Rosenau T (2021) *Monatsh Chem* 152:1231
- Patel A, Liebner F, Netscher T, Mereiter K, Rosenau T (2007) *J Org Chem* 72:6504
- Adegoke GO, Vijay Kumar M, Gopala Krishna AG, Varadaraj MC, Sambaiah K, Lokesh BR (1998) *J Food Sci Technol* 35:283
- Ding T, Li T, Li J (2019) *ACS Appl Mat Interfaces* 11:6463
- Wendler F, Meister F, Heinze T (2005) *Macromol Symp* 223:213
- Britton J, Davis R, O'Connor KE (2019) *Appl Microbiol Biotechnol* 103:5957
- Quiles JL, Ramírez-Tortosa MC, Yaqoob P (eds) (2006) *Olive oil and health*. CABI Publishing, Wallingford
- Peltzer M, Navarro R, López J, Jiménez A (2010) *Polym Degrad Stab* 95:1636
- Fortunati E, Luzi F, Fanali C, Dugo L, Belluomo GM, Torre L, Kenny JM, Santi L, Bernini R (2017) *J Renew Mat* 5:81
- Haddar W, Baaka N, Meksi N, Ticha MB, Guesmi A, Mhenni MF (2015) *Fibers Polym* 16:1506
- Bayraktar O (2018) *Textile Leather Rev* 1:90
- Elder T, Del Río JC, Ralph J, Rencoret J, Kim H, Beckham GT, Crowley MF (2020) *ACS Sustain Chem Eng* 8:11033
- Yamauchi F, Ito T, Kawamoto O, Komatsu T, Akiyama T, Yokoyama T, Matsumoto Y (2020) *Holzforchung* 74:559

60. Miyagawa Y, Tobimatsu Y, Lam PY, Mizukami T, Sakurai S, Kamitakahara H, Takano T (2020) *Plant J* 104:156
61. Zaccaron S, Ahn K, Henniges U, Potthast A, Rosenau T (2022) *Cellulose* 29:3733
62. Hosoya T, Bacher M, Potthast A, Elder T, Rosenau T (2018) *Cellulose* 25:3797
63. ISO 2470-1 (2009) Measurement of diffuse blue reflectance factor—Part 1: indoor daylight conditions (ISO brightness). International Organization for Standardization, Geneva
64. Brightness loss of pulp. TAPPI method UM 200 (2012) TAPPI, Peachtree Corners, GA
65. Standard Testing Methods. Paptac E.4P (2012) Pulp and Paper Technical Association of Canada. Brossard (Quebec), Canada
66. IUPAC-IUB Commission on Biochemical Nomenclature (CBN) (1982) *Eur J Biochem* 123:473
67. IUPAC-IUB Commission on Biochemical Nomenclature (CBN) (1974) *Arch Biochim Biophys* 165:1
68. Urano S, Hattori Y, Yamanoi S, Matsuo M (1980) *Chem Pharm Bull* 28:1992
69. Brownstein S, Ingold KU (1989) *J Org Chem* 54:560
70. Urones JG, Marcos IS, Cubillo L, Garrido NM, Basabe P (1990) *Phytochem* 29:2223
71. Yamauchi R, Matsui T, Kato K, Ueno Y (1990) *Agric Biol Chem* 54:2703

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.